Development of Metal Hydrides at Sandia National Laboratories

Presented by

Jim Wang

Sandia National Laboratories

Livermore, California

May 23, 2005

This presentation does not contain any proprietary information

Project ID# STP62

Overview

Timeline

- Project started in the early 1990s'
- Reviewed and renewed every FY through Annual Operation Plans
- Incorporated into MHCoE January 2005
- Percent complete ~ 50% for FY05

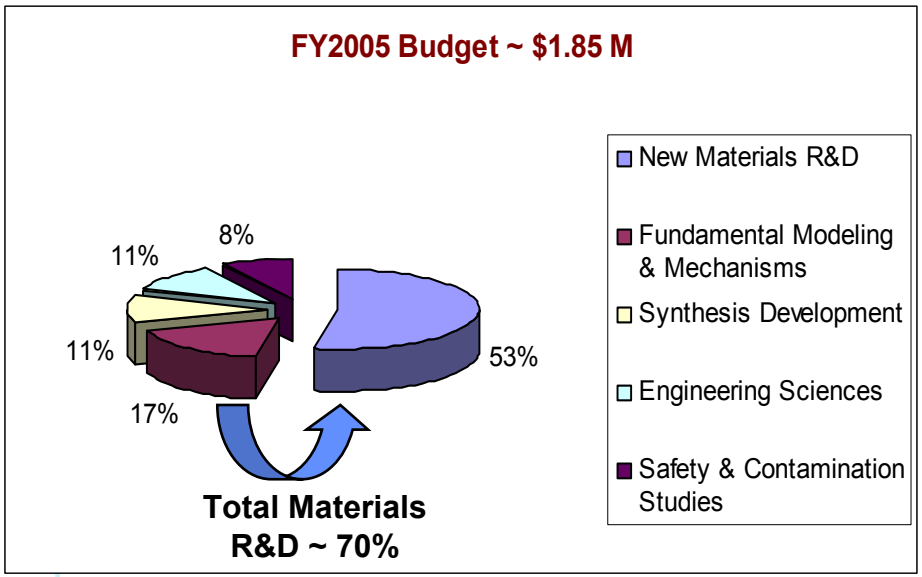

Barriers

MYPP Section 3.3.4.2.1 On-Board Storage Barriers

- **A. – G.** Cost, Weight & Volume, Efficiency, Durability, Refueling Time, Codes & Standards, Life Cycle & Efficiency Analyses
- **M.** Hydrogen Capacity and Reversibility
- **N.** Lack of Understanding of Hydrogen Physisorption and Chemisorption
- **O.** Test Protocols and Evaluation Facilities
- **P.** Dispensing Technology

Partners

- MHCoE collaborators include Caltech, ORNL, JPL, UNR, Stanford U, U of Utah, U Hawaii, U of PITT, SRNL, HRL, UIUC, CMU, GE, NIST, BNL, Intematix
- Gary Sandrock operates IEA/Task-17, maintains the Hydride Information Center databases and collaborates with BNL
- Singapore U., Tohoku U., UCLA, U. Geneva, LLNL

Objectives

- *Develop new reversible hydrogen storage materials that meet or exceed DOE FreedomCAR 2010 and 2015 goals,*
- *Identify reversible hydrides that exceed the hydrogen capacity of Mg modified Li amides in FY05.*

Sandia Team (~ 6 FTEs)

Ray Baldonado
Bob Bastasz
Tim Boyle
Yongkee Chae
Paul Crooker*
Sherrika Daniel*
Karl Gross (consultant)
Steve Karim
Jay Keller
Weifang Luo
Eric Majzoub
Tony McDaniel
Marcina Moreno
Vidvuds Ozolins (consultant)
Ewa Ronnebro*
Gary Sandrock (consultant)
Ken Stewart
Roland Stumpf
Konrad Thuermer
Jim Voigt
Karl Wally*
Jim Wang
Ken Wilson
Nancy Yang

* New Team Members

Approach

Science-based materials development

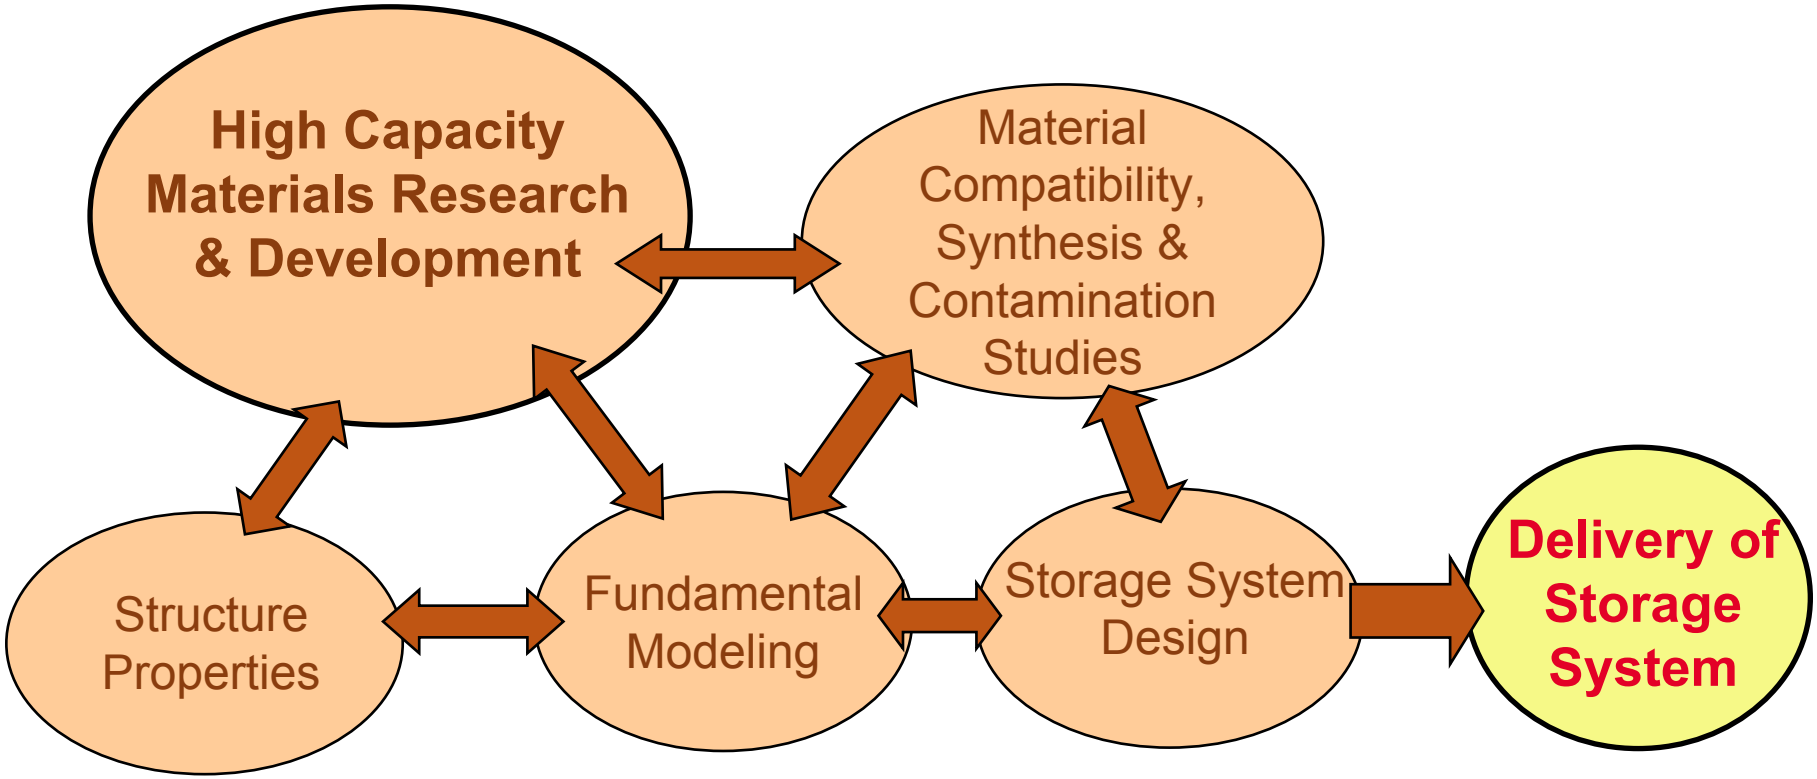

I. New Hydrogen Storage Materials

A. *Low temperature Mg modified Li amides*

Amide : $-NH_2$, $LiNH_2$ | **Imide : $>NH$, Li_2NH** | **Nitride : $\equiv N$, Li_3N**

1st Step:

$$LiNH_2 + LiH \underset{1\ atm}{\overset{300^oC}{\rightleftharpoons}} Li_2NH + H_2$$

6.5 wt%

2nd step:

$$Li_2NH + LiH \underset{0.05\ atm}{\overset{300^oC}{\rightleftharpoons}} Li_3N + H_2$$

5 wt%

Two steps in total:

11.5 wt%

Major limitations:

- Temperature too high
- Pressure too low

Chen, P. et al, *Nature* vol. **420**, (2002) 302.

New system:

Partial Mg substitution

W. Luo, J. Alloys and Comp., 381 (2004) 284-287.

Y. Nakamori, S. Orimo, J. Alloys and Compounds, 370 (2004) 271-275.

(A1)Thermodynamic characterization - Luo

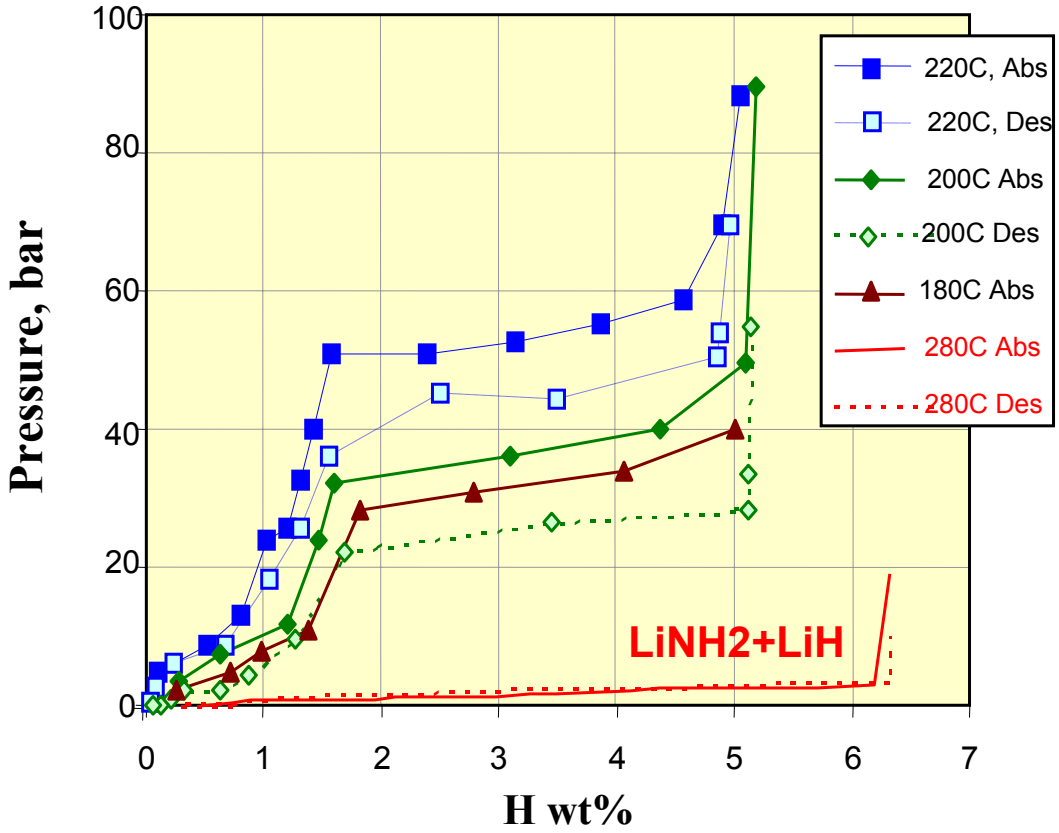

Isotherms were measured at:

- 220, 200, 180°C for absorption and desorption.
- Plateau pressure much higher than the one without Mg-substitution.

(A2) Sorption profile - Luo

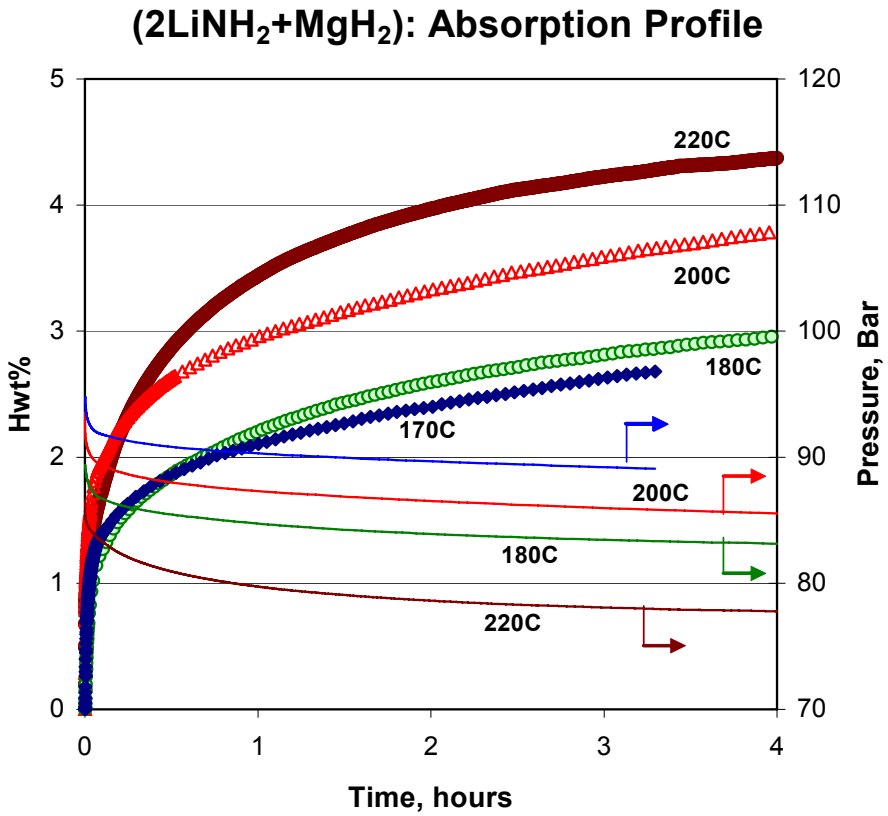

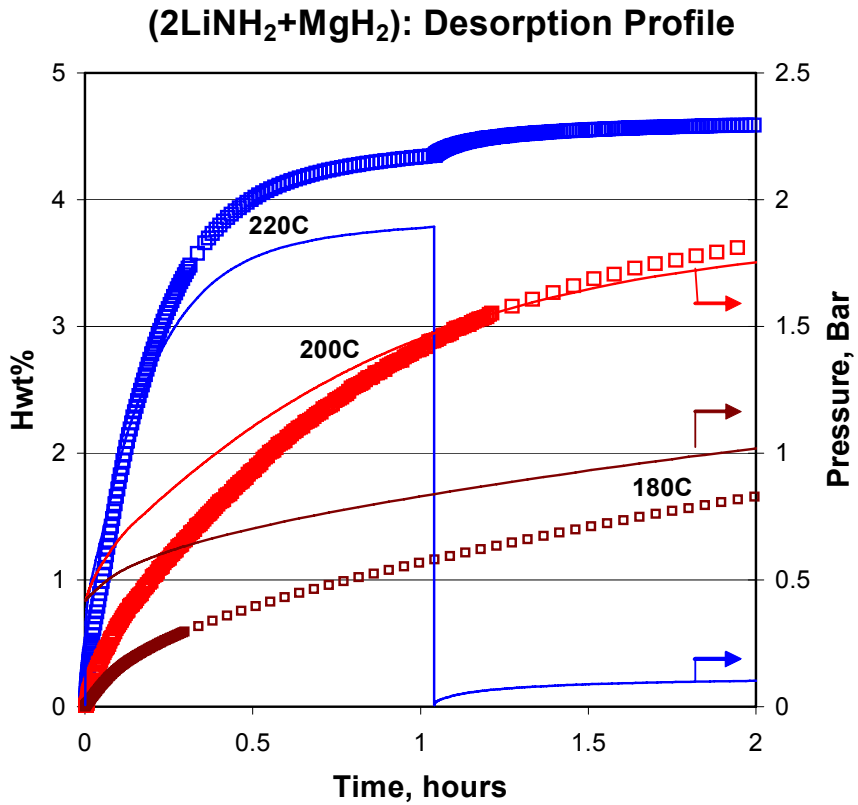

- *85% of desorption completed in 0.5h at 220°C*
- *Sorption rate decreases with decreasing temperature*

(A3) XRD characterization - Luo & Majzoub

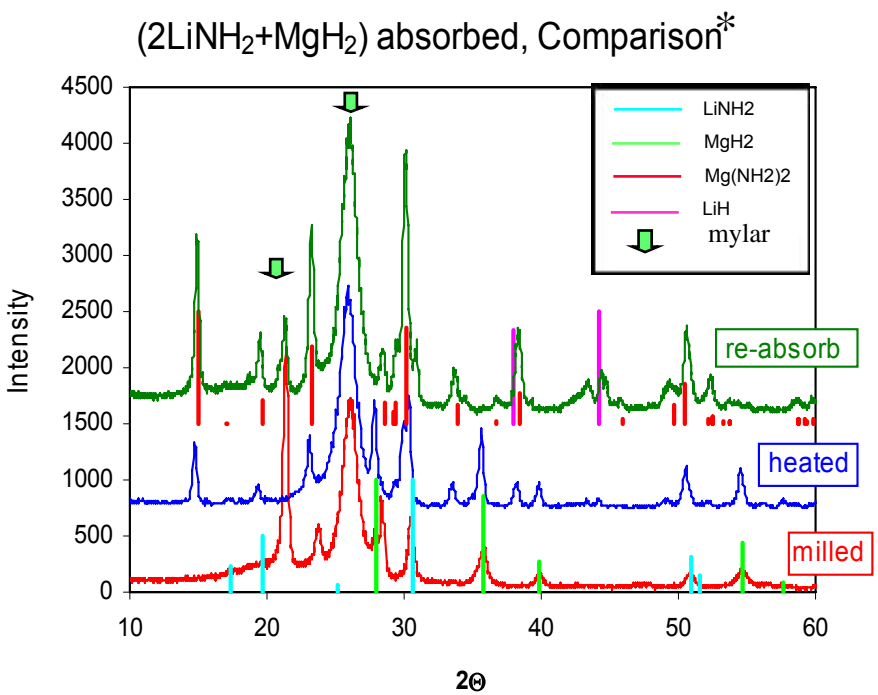

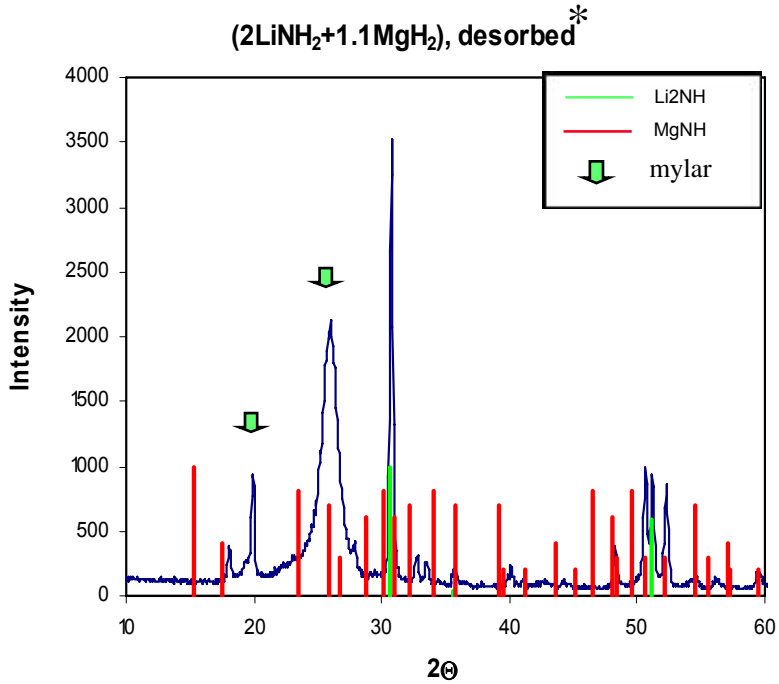

* Mylar was used to protect sample from being contaminated during XRD scanning

A new reaction path was proposed based on the material characterization results:

$$2LiNH_2 + MgH_2 \longrightarrow Li_2Mg(NH)_2 + 2H_2 \rightleftharpoons 2LiH + Mg(NH_2)_2$$

(A4) Diffuse Reflectance Infrared Spectroscopy Measurements– McDaniel & Chae

- First desorption cycle material "as milled"
- Second desorption cycle followed H_2 adsorption
  - 8 MPa
  - 473 K
  - 120 minutes
- H_2 desorption
  - 130 KPa
  - 5 K min^{-1} ramp

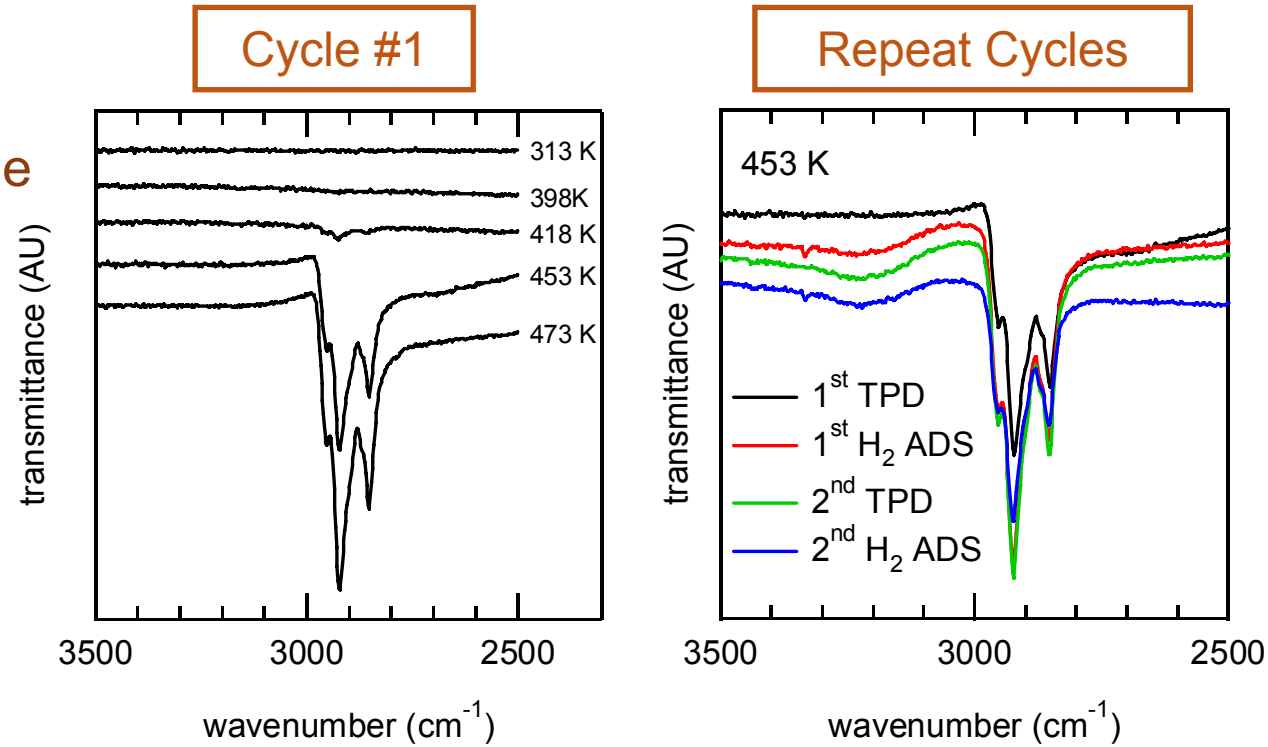

N-H vibrational features appeared upon first heating of freshly milled sample. Structural changes in material stabilized on subsequent ads-des cycles.

(A5) Desorbed gas analysis– Luo

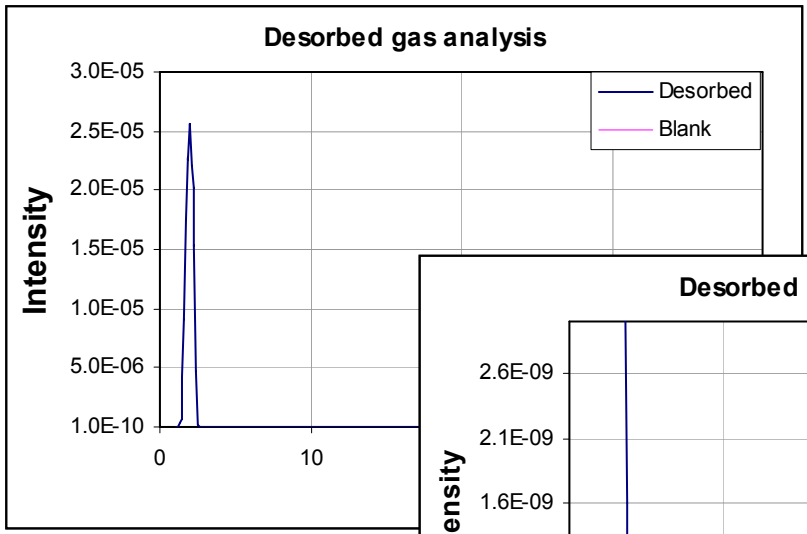

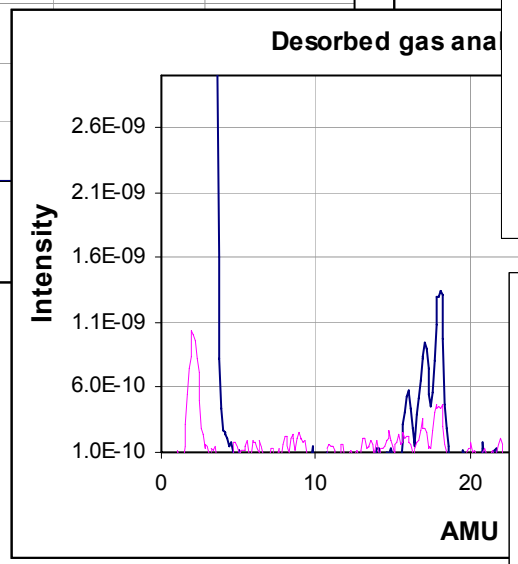

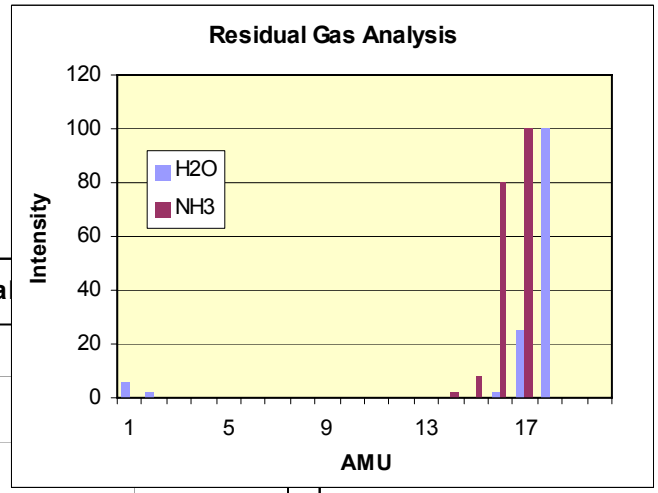

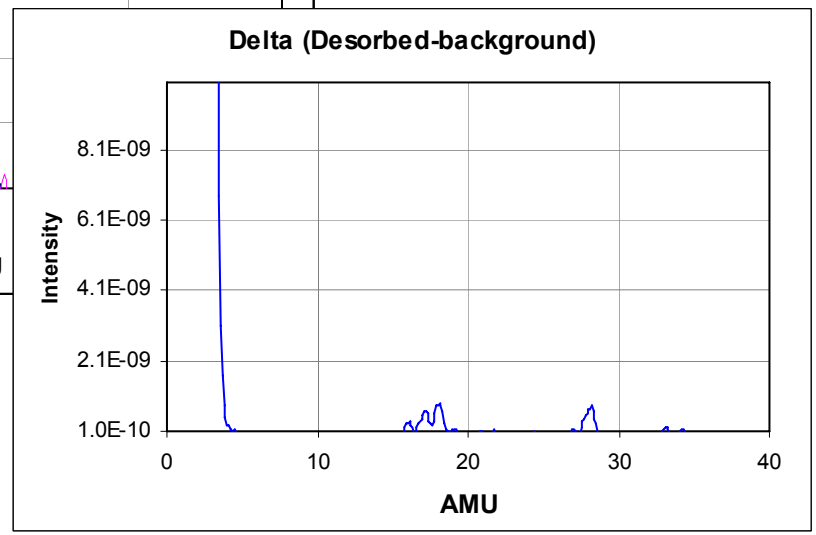

NH_3 in desorbed gas was found to be < 40 ppm

(A6) Ammonia Issues - Luo

- Ammonia formation:
  - *Is possible from self-decomposition of amide at higher temperatures than hydrogen formation*
  - *Could be inhibited by thorough mixing with sufficient amount of hydrides*
- Potential methods to eliminate ammonia formation:
  - *Optimize operational temperature*
  - *Optimize amide/hydride ratio*
- Potential methods to remove ammonia in H_2 stream:
  - *Add ammonia filter or trap before enter fuel cell system*

Ammonia desorption can be controlled by engineering design

(A7) Cycle test to 101 cycles - Gross

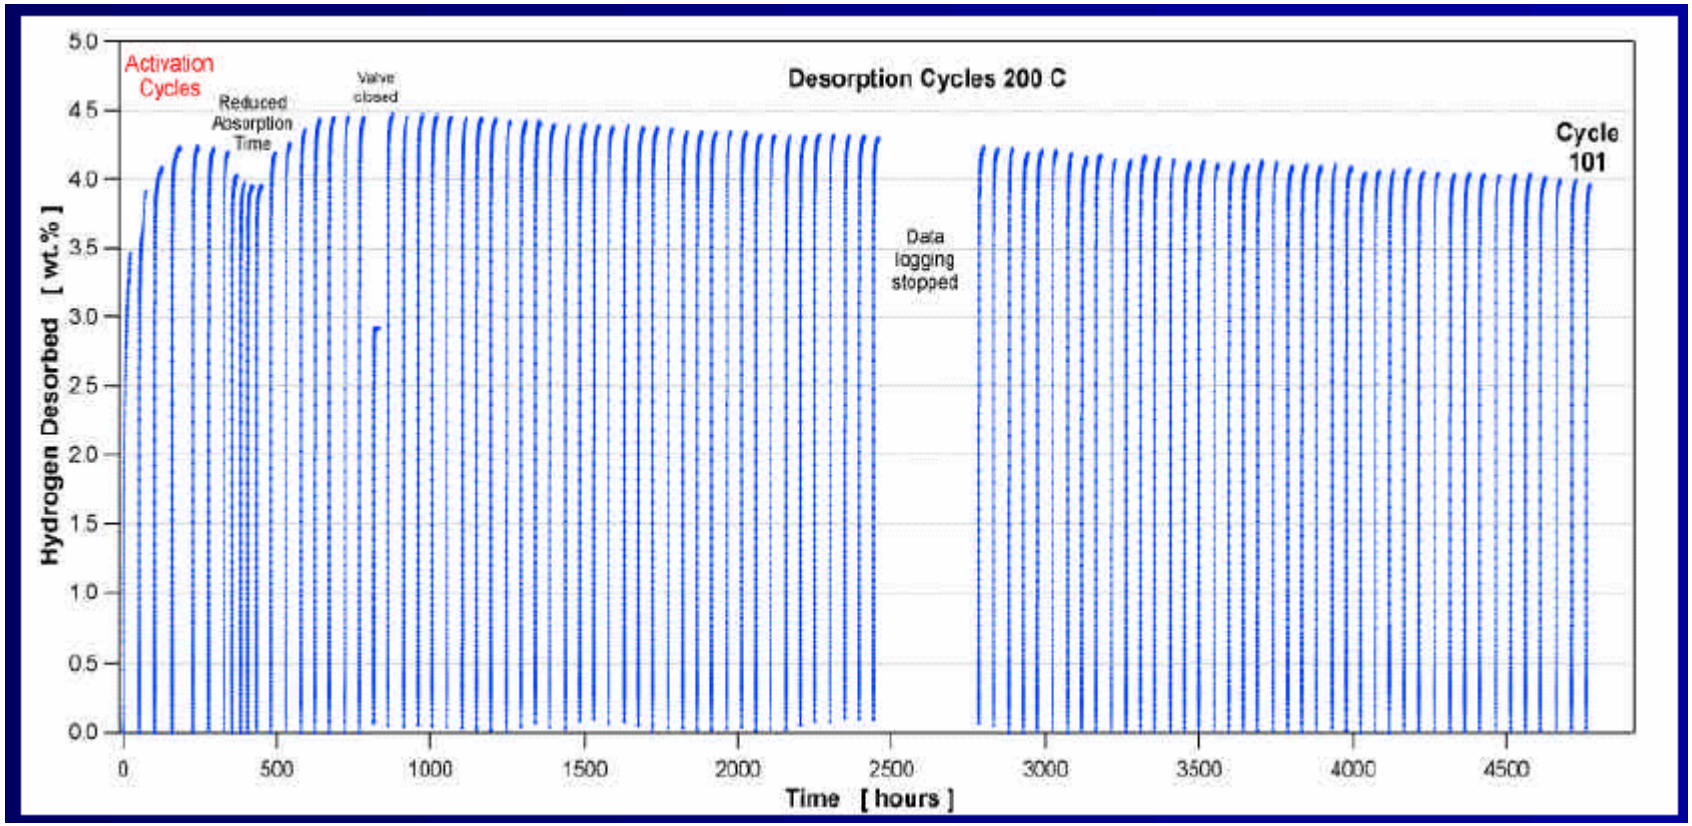

Capacity loss: 0.005wt% per cycle

(A8) Thermal Properties Measurements
Hardware configuration – Crooker & Dedrick

Loaded with ~ 130 grams ball-milled $LiNH_2$-MgH_2

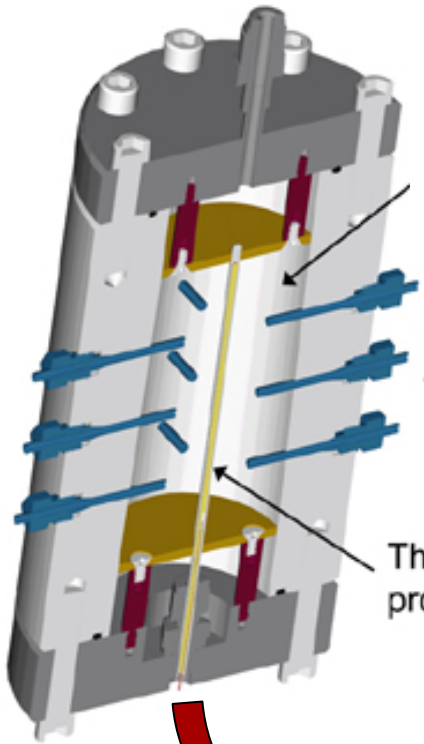

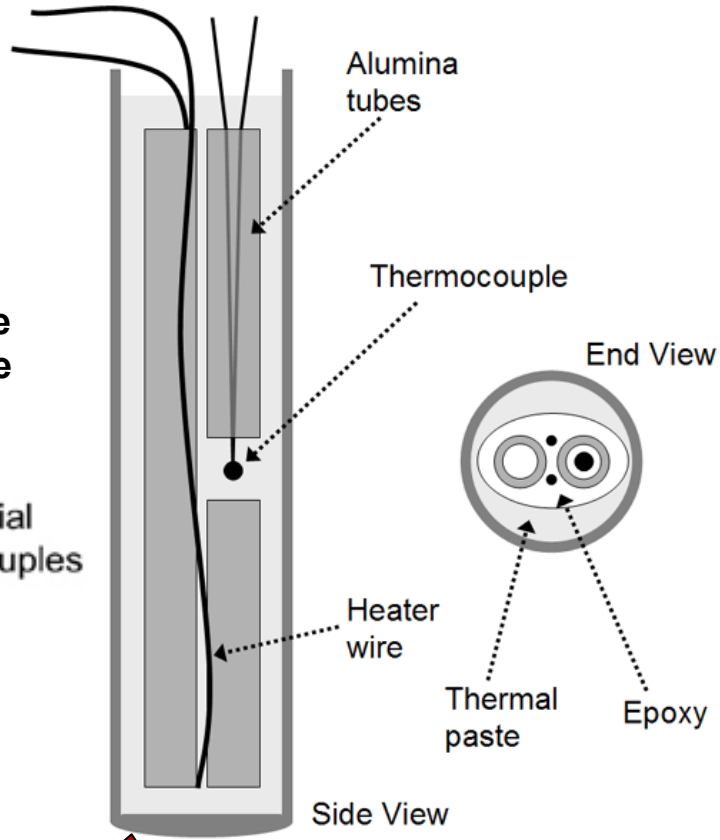

Optimized to measure K_{th} up to ~5 W/m-K

Solid model → Probe design

(A9) Preliminary K^{th} results – Crooker

$$2LiNH_2 + MgH_2 \longrightarrow Li_2Mg(NH)_2 + 2H_2 \rightleftharpoons 2LiH + Mg(NH_2)_2$$

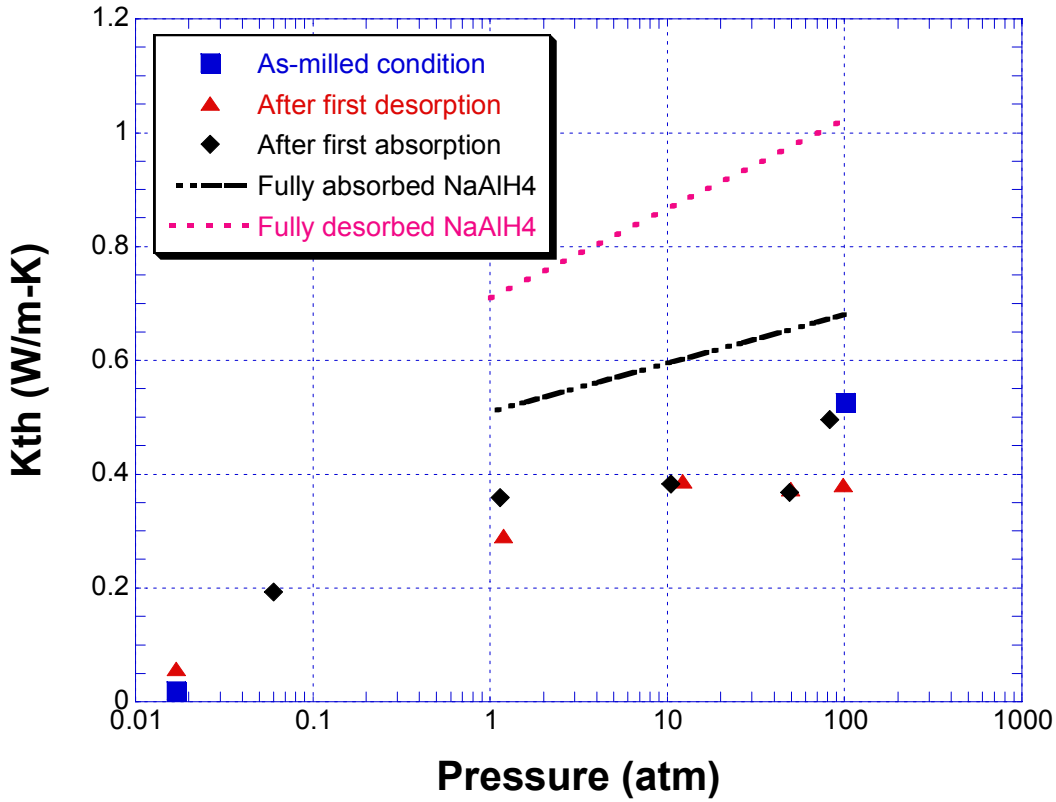

Thermal conductivity of $LiNH_2$+MgH_2 material increases with gas pressure and similar to those of sodium alanates.

B. Modified Complex Hydrides
Investigation of bi-alkali alanates

- Pressed pellets of hand mixed or ball milled samples were tested at high pressures up to 136 MPa and temperatures up to 450C facility.
- bi-alkali alanates of various molar ratios were tested:
  - *Li-K, Li-Mg, Li-Ca, Li-Ti, Mg-Ti, etc….*
  - *New bi-alkali Li-K alanate formed @ 68 MPa and 330C*
    - *Starting mixture of LiAlH4 + 2KH or LiH + 2KH + Al*
    - *Pellets expanded and showed in white color*
- Investigation of Li(Al1-xBx)H4, Na(Al1-xBx)H4, etc…systems are in progress

Properties of new Li-K alanates - Ronnebro

Powder X-ray diffraction pattern

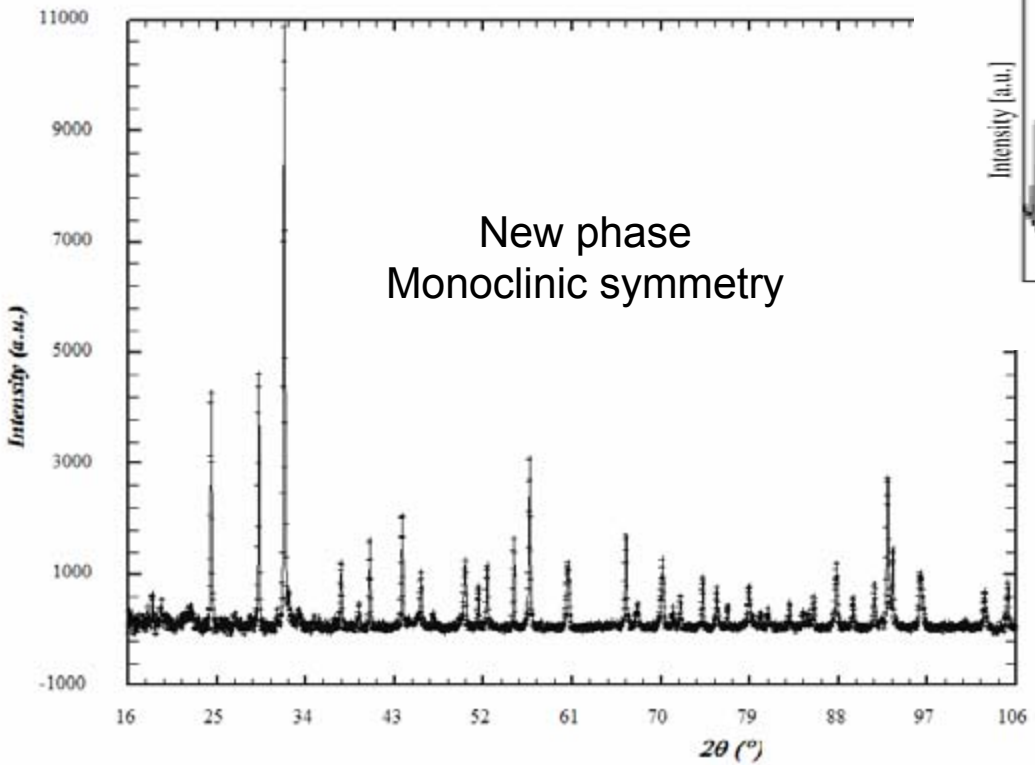

New phase
Monoclinic symmetry

Raman spectra

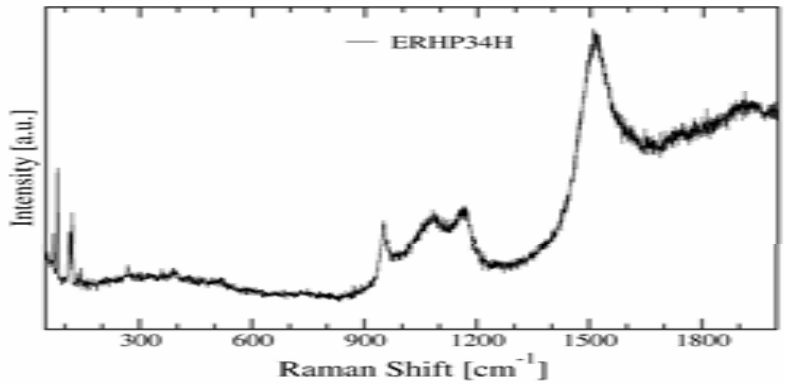

FTIR

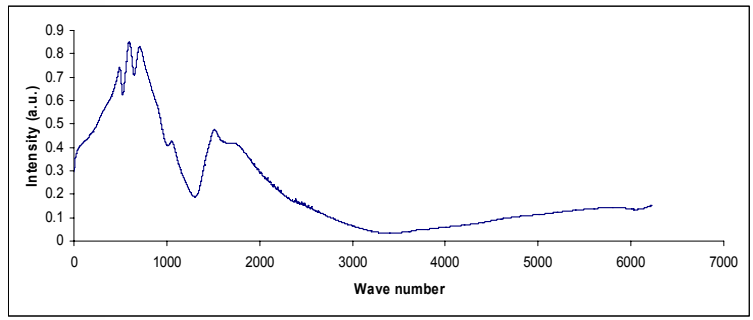

Structural, kinetic and thermodynamic properties are under investigation

C. Modified Borohydrides

(*collaboration between Sandrock & BNL)*

Can Hydrogen Driven Metallurgical Reactions be used to make nanocomposites for "stimulating" the Borohydrides?

$LiBH_4 \Leftrightarrow LiH + B + 3/2\ H_2$ (13.9 wt. % H)

$NaBH_4 \Leftrightarrow NaH + B + 3/2\ H_2$ (8.0 wt. % H)

Possible Oxide Precursor Reactions (schematic):

$NaBH_4 + MoO_3 \Rightarrow NaBH_4 + Mo + (Na_2O \text{ or } B_2O_3 \text{ or } H_2O)$

$NaBH_4 + Mo \Leftrightarrow NaH + MoB_x + H_2$

Effect of Mo & MoO_3 on NaBH4 - Sandrock

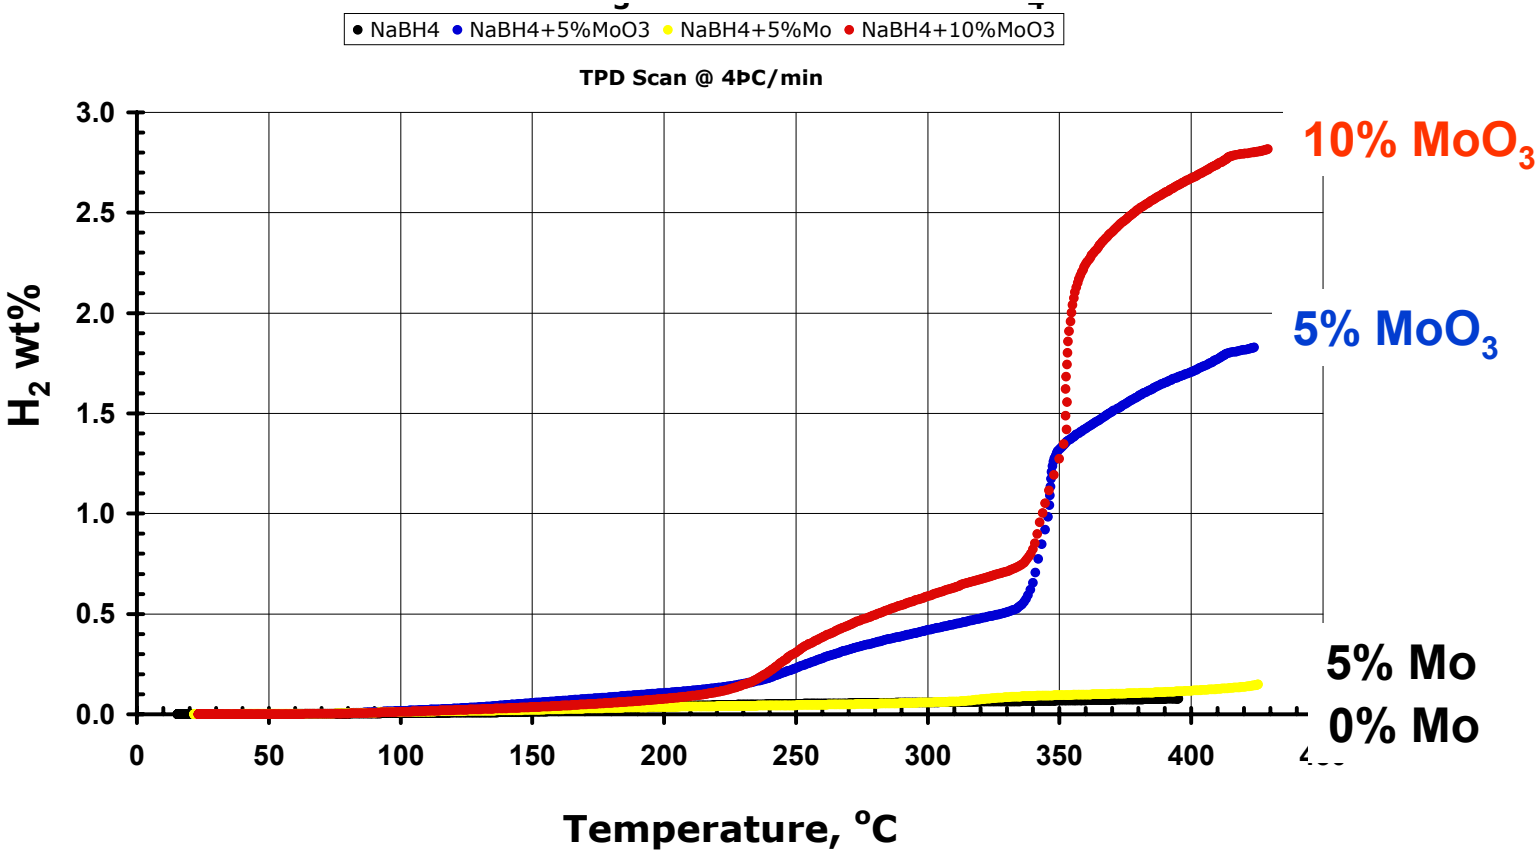

Mo is not the best addition for $NaBH_4$ reversibility because the Mo-borides are too stable.

D. Destabilized Mg hydride – Gross
(in collaboration with HRL)

MgH_2 Has 7.6 wt.% hydrogen - but too stable for FCV applications

Much more favorable thermodynamics: $2MgH_2 + Si \Rightarrow Mg_2Si + 2H_2$

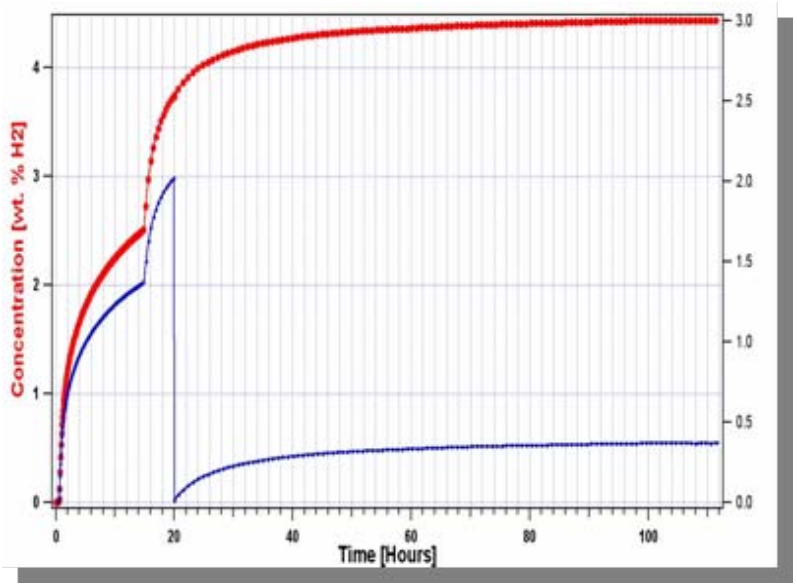

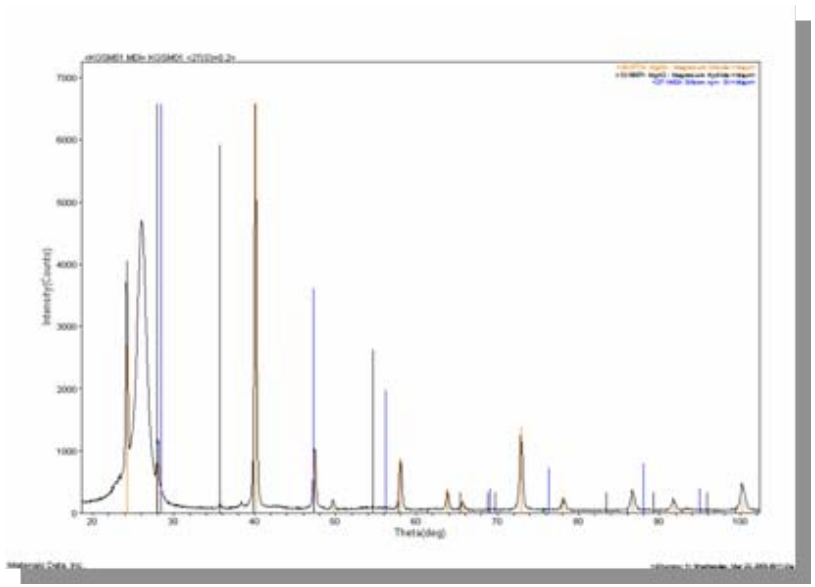

- *Reversibility being tested using High-pressure station*
- *4.5 wt% hydrogen was release on desorption at 360°C*
- *XRD after desorption showed 100% conversion to Mg_2Si*

E. Aluminum hydrides (AlH_3)

(collaboration of Sandrock & BNL)

$$\alpha\text{-}AlH_3 \longrightarrow Al + 3/2\ H_2$$

H-capacity (g) = 10.1 wt%

H-capacity (v) = 149 kg/m^3

ΔH_{des} = 7.6 kJ/mol H_2

AlH$_3$

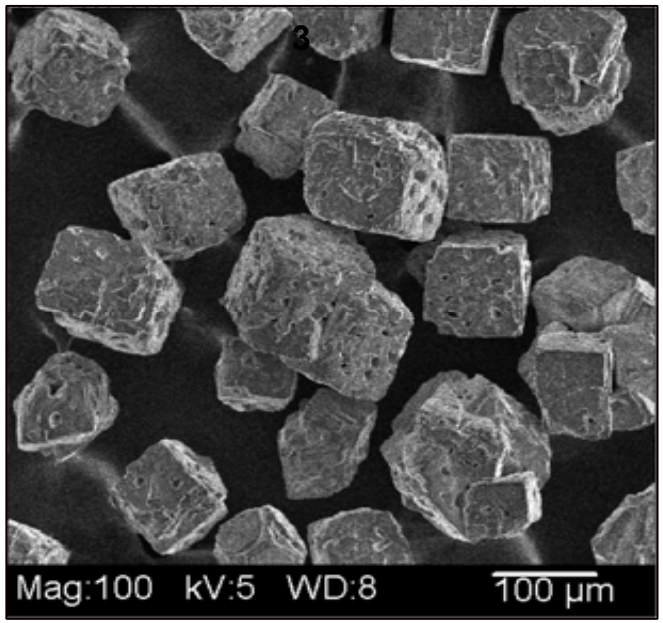

Depleted Al

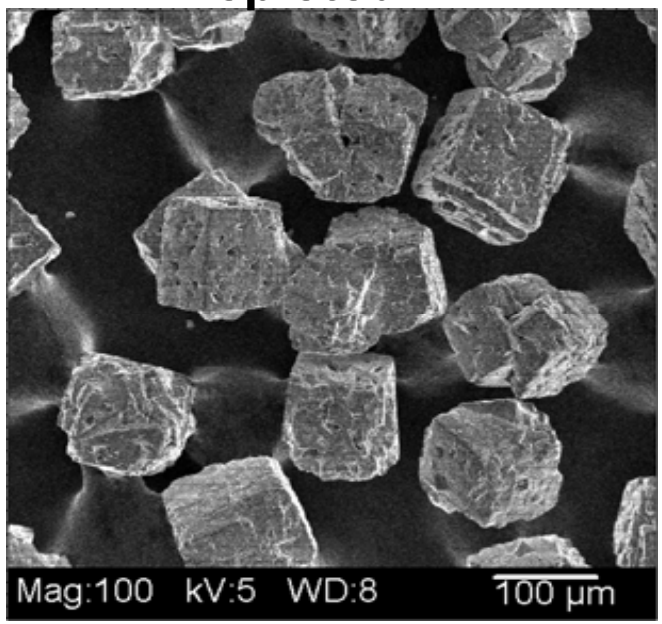

Effect of LiH doping via TPD – Sandrock

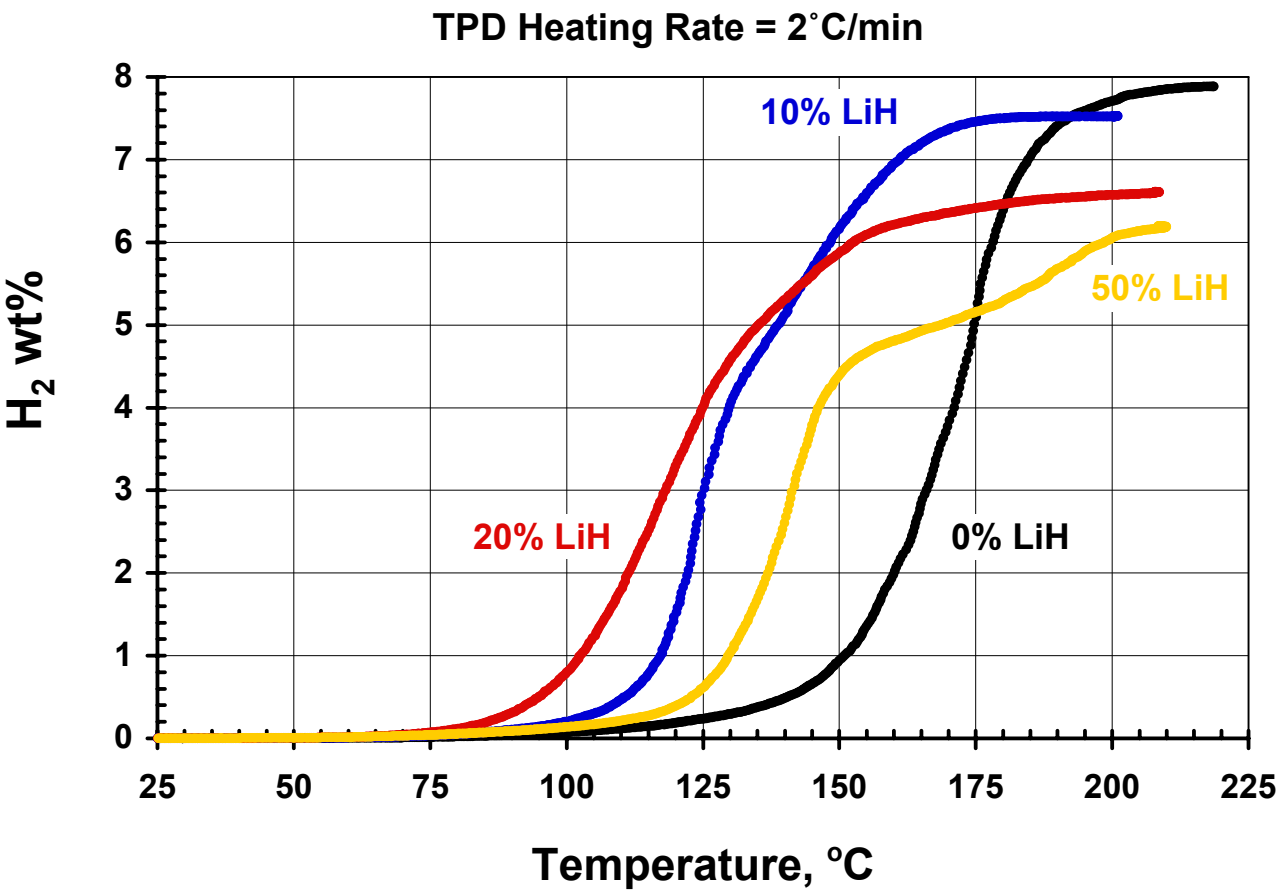

Desorption temperature can be reduced by adding more LiH

II. Fundamental Mechanisms & Modeling

(1) Surface alloy catalytic model of $NaAlH_4$ - Stumpf

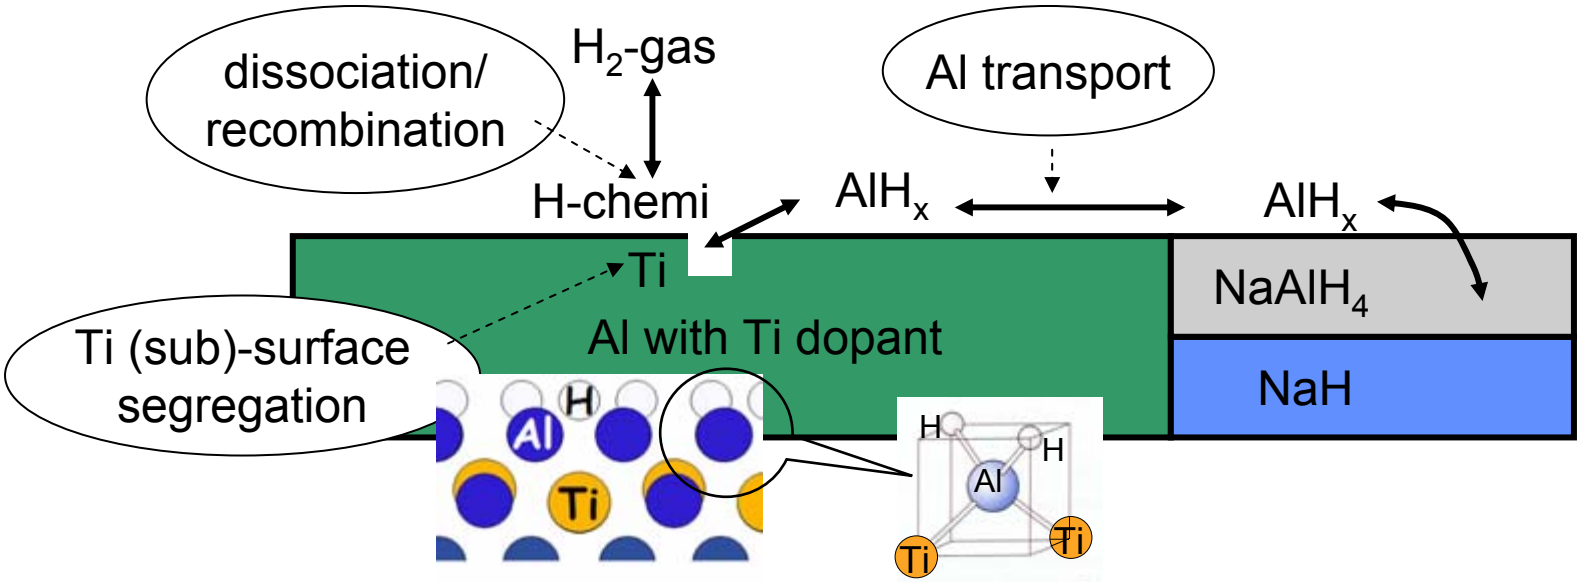

- H_2 chemistry is autocatalytic: H promotes (sub-) surface Ti
- Sub-surface Ti creates "activated" sp3-like Al surface atoms with stronger H affinity and reduced H_2 sorption barriers
- Exposed Ti offers chemisorbed H_2 binding site and vanishing barriers
- AlHx provides long range Al transport
- Results for Sc are similar to those for Ti

Surface alloys of simple and transition metals are promising new catalysts for H chemistry

(2) Effect of H_2 or H ? - Majzoub & Stumpf

Experimental support for surface mechanism: dosing of Al+NaH with "atomic" H

Idea: use Pd surface to crack H_2

- *X-ray diffraction after 10 day exposure of Al+NaH to H_2 in contact with Pd foil shows 10% of Al+NaH converts to Na_3AlH_6 and $NaAlH_4$*
- *Control experiment without Pd shows < 1% alanate formation*

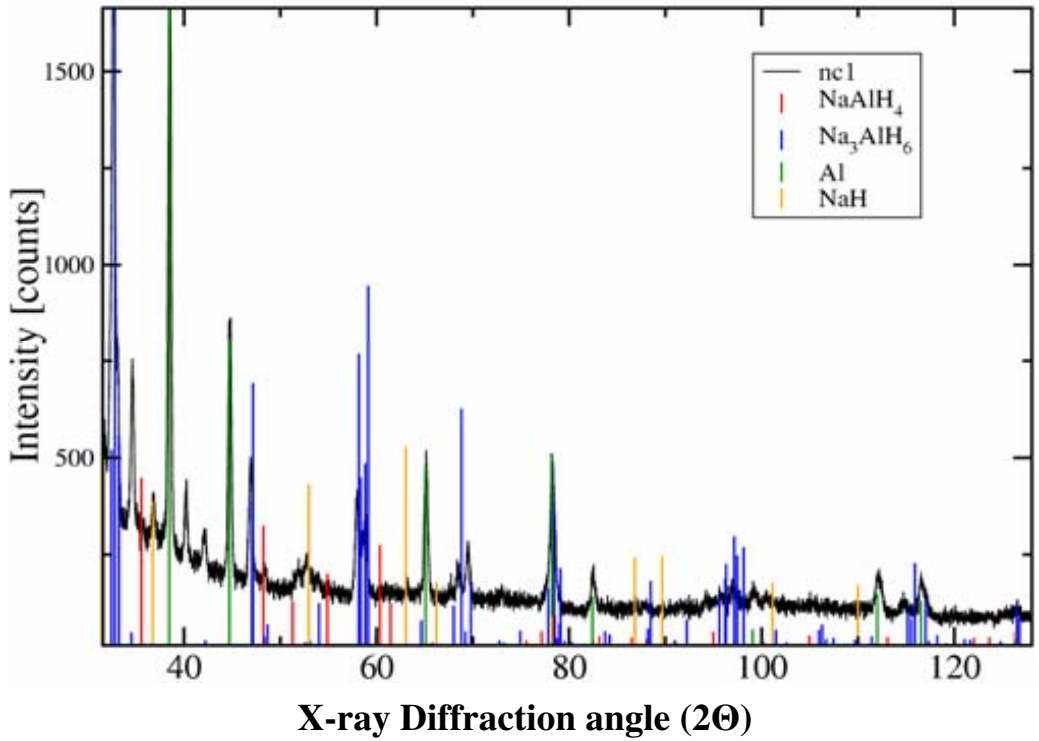

H_2 cracking ability of Pd helps hydride formation

(3A) Where is Ti ? - Bastasz

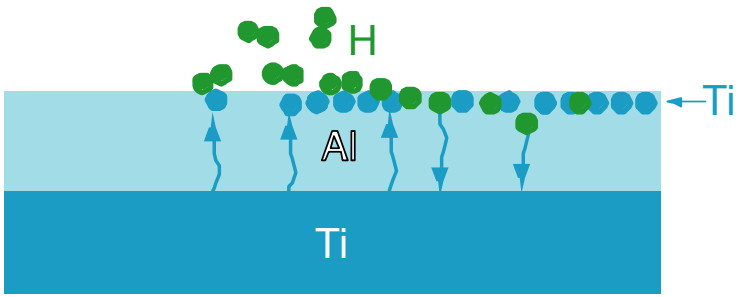

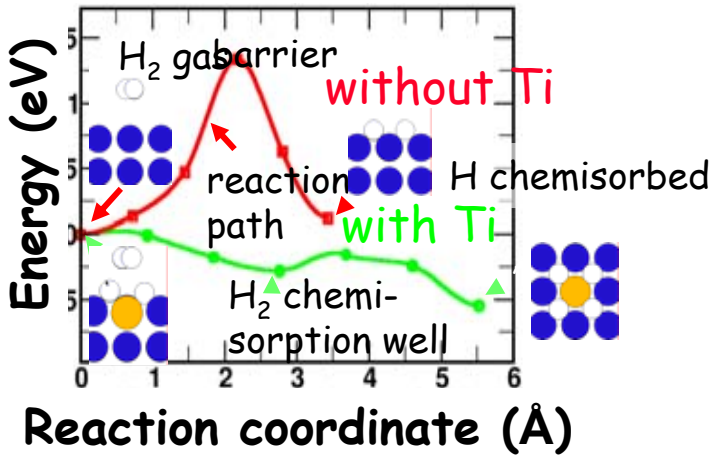

H may stabilize Ti on Al surfaces – Predictions:

- *H on surface promotes Ti segregation to near-surface sites*
- *Ti reduces H_2 adsorption barriers on Al to a fraction of an eV.*
- *Ti facilitates both uptake and release of H_2.*

Is there experimental evidence for this?

(3B) Model validation - Bastasz

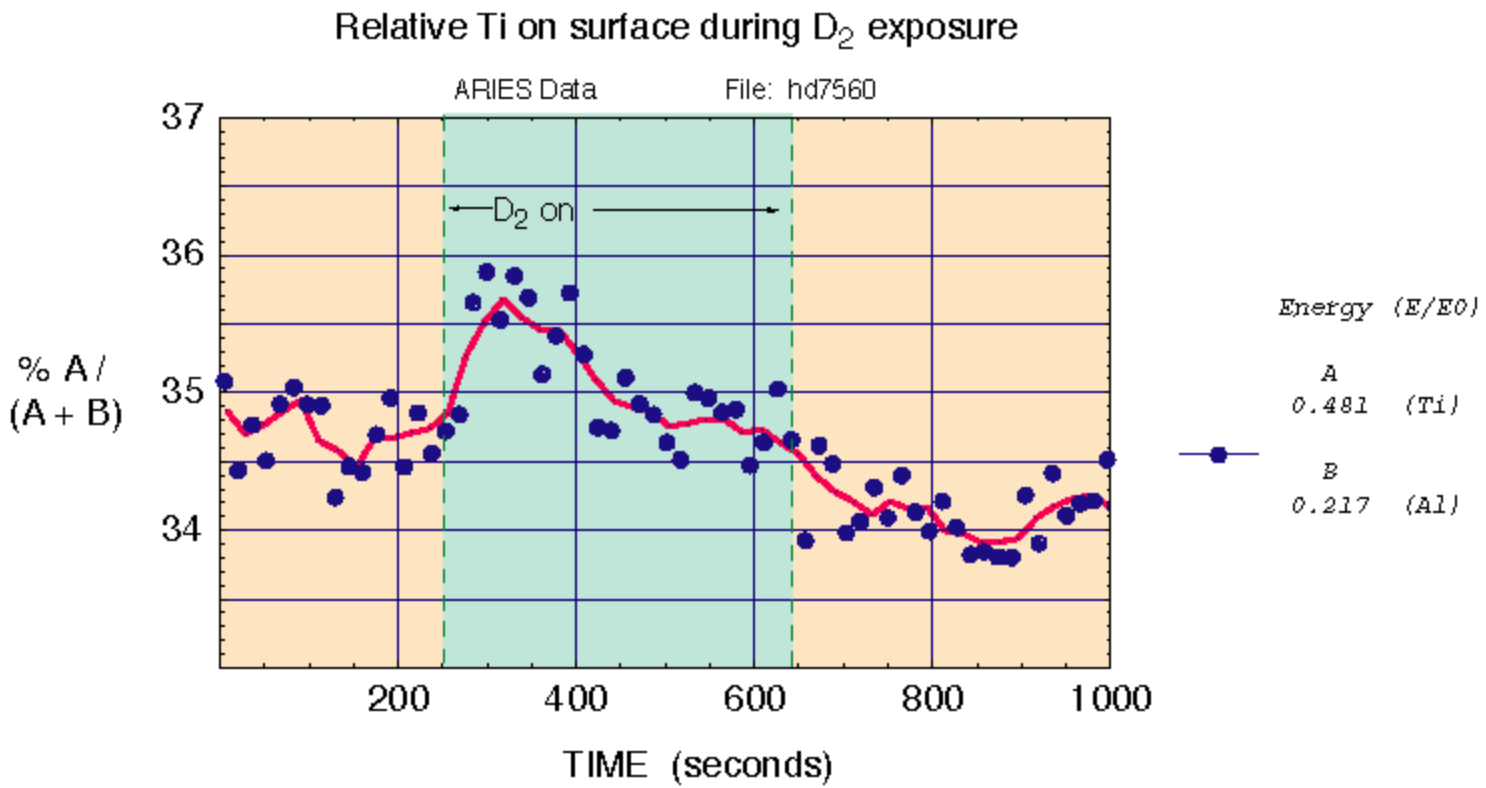

Ti/(Ti+Al) signal ratio changes indicating that Ti concentration on the surface appears to increase upon exposing sample to D_2.

(4) In-Situ Raman spectra observations - Majzoub

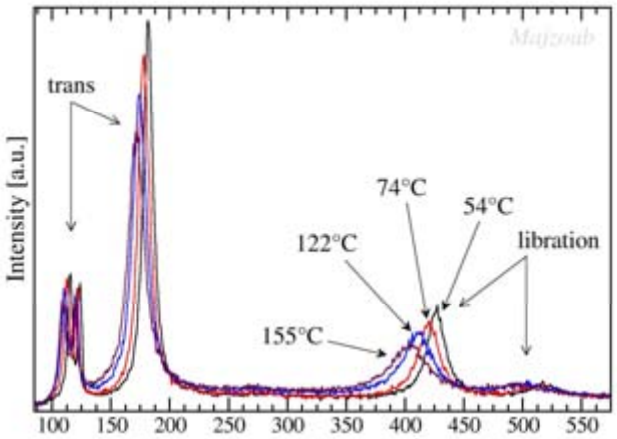

- Crystal modes soften up to 6-7% at Tm
- AlH_4 anion modes soften less than 1.5%
- AlH_4 anion is also stable in the melt!

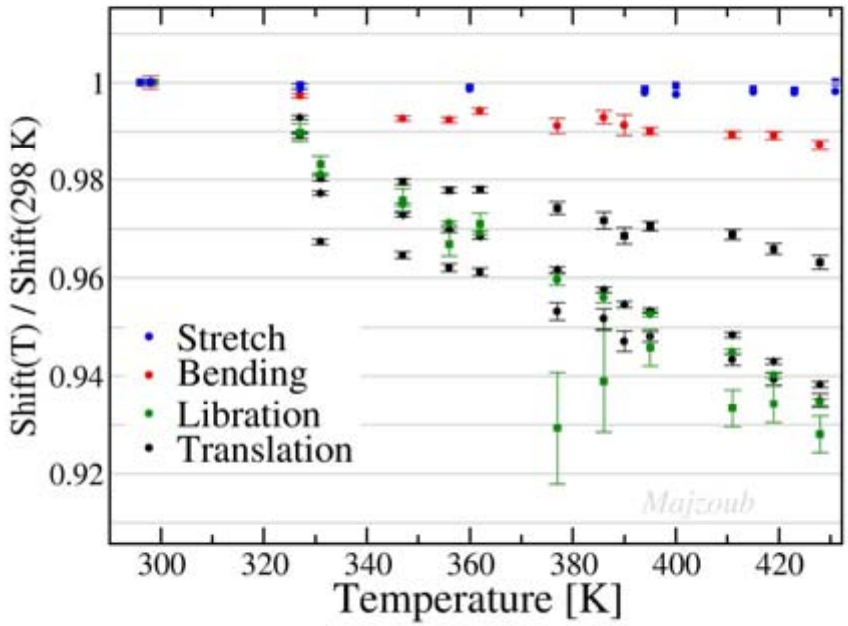

Data shows a very stable AlH_4 anion.

III. Synthesis of Nanostructured Materials

Wet chemistry synthesis using NH_3 – Daniel & Boyle

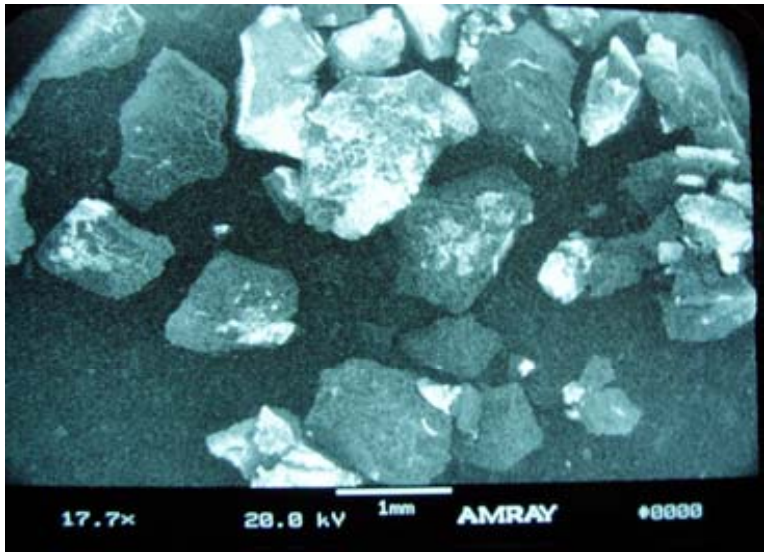

Fig. 1

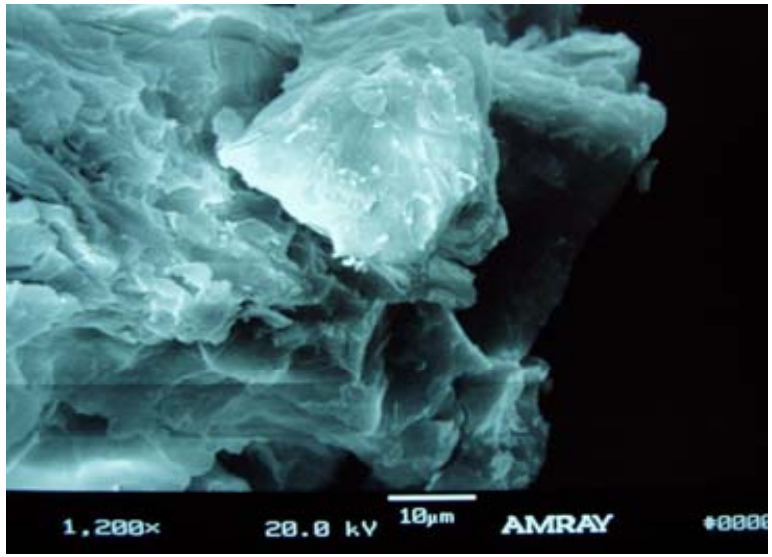

Fig. 2

Scanning Electron Microscopy (SEM) images of $Mg(NH_2)_2$ show the particle size to be ~1-2 mm. The morphology appears coarse and brittle which can be easily broken or ground.

However, poor performance was observed due to contamination of residue solvents from wet chemistry processing.

Responses to Previous Year Reviewers' Comments

1. Overall Project Score: 3:32 – *positive feedbacks validated our approach and accomplishments in FY2004.*
2. Not enough progress made toward development of onboard storage module – *we will start the storage module development later this FY and gradually increase its efforts as the program progresses toward Phase II.*
3. Primary empirical approach to new material discovery – *we selected our tested materials based on thermodynamics, atomistic modeling and experiences (teaming between modeling and experimentation).*
4. Cost estimation is not covered – *we will initiate cost study as one of system studies in parallel to the materials discovery efforts.*
5. Difficulty of geographic separation – *we established on-line, instant communication system and regular teleconferences and face-to-face meetings for all Center partners.*

Responses to Previous Year Reviewers' Comments (continued)

6. System-based studies are needed – *we started the Center (in Jan) with engineering system as a central focus, with a ramp up of the engineering design in phase II.*
7. Make sure the performance metrics include considerations of (1) "whole storage system" weights and volumes and (2) "net" energy delivered to the vehicle – *we used this to screen our material candidates as a part of our Center system-based approach.*
8. Schedule down select of materials – *yes, we have go/no-go decision points in our AOP milestones as well as our MHCoE plan.*
9. Investment in Na-alanates? – *we stopped most tests on Na-alanates except some experiments to validate our 1st principle model.*

Future Work

Remainder of FY2005

- New Storage Materials Development
  - *Explore new complex hydrides via HP/HT process*
  - *Optimize Li-Mg-H based materials for faster kinetics and lower temperatures*
  - *Search for storage materials with optimal properties*
- Fundamental Mechanisms
  - *Conclude the modeling validation experiments on alanates*
  - *Initiate modeling and mechanisms studies on Li-Mg-H, B-Li-H and Al-H based materials*
- Chemical Synthesis Development
  - *Improve the wet chemistry process to produce pure storage materials with nano-size particles*
- Engineering Science of Complex Hydrides
  - *Continue to measure engineering properties of hydrogen storage materials, e.g., thermal conductivities, volume expansion, tap density,…..etc.*
  - *Continue to study performance degradation and reliability of candidate storage materials*
  - *Initiate investigation on reactions related to safety*
- Collaboration with MHCoE Partners
  - *Lead the Metal Hydride Center of Excellence.*

Future Work

FY2006 and beyond

- New Storage Materials Development
  - *Continue to search for materials with optimal storage properties*
- Fundamental Mechanisms
  - *Continue to model newly discovered materials*
  - *Develop models to predict new materials and to guide experiments*
- Chemical Synthesis Development
  - *Continue to develop processes to produce storage materials with nano-size particles.*
- Engineering Science of newly developed Hydrides
  - *Continue to build engineering property database of hydrides.*